



Physical and Mechanical Properties of Heat Treated *Daniella oliveri* (Africa Balsam Tree) Wood

**Ebenezer Adeyemi Iyiola^{1*}, Babatola Olufemi¹, Victoria Olubukola Oyerinde¹,
J. M. Owoyemi¹ and Ayanleye Samuel¹**

¹*Department of Forestry and Wood Technology, Federal University of Technology, P.M.B. 704, Akure, Nigeria.*

Authors' contributions

This work was carried out in collaboration among all authors. Author EAI designed the study, performed the experiment and statistical analysis. Authors BO and VOO wrote the protocol and wrote the first draft of the manuscript. Author AS modified and edited the final draft. All authors read and approved the final manuscript.

Article Information

DOI: 10.9734/CJAST/2019/v35i230175

Editor(s):

(1) Dr. Umar Nirmal, Senior Lecturer, Centre of Advanced Mechanical and Green Technology, Faculty of Engineering and Technology, Multimedia University, Malaysia.

Reviewers:

(1) Charles Chinwuba Ike, Enugu State University of Science and Technology, Nigeria.

(2) R. M. G. Rajapakse, University of Peradeniya, Sri Lanka.

(3) Rosario García Giménez, Autonomous University of Madrid, Spain.

Complete Peer review History: <http://www.sdiarticle3.com/review-history/48727>

Received 16 February 2019

Accepted 27 April 2019

Published 03 May 2019

Original Research Article

ABSTRACT

Aims: This work investigated the effect of thermal modification on some of the physical properties and mechanical properties of *Daniella oliveri* wood.

Study Design: The study design used for this experiment was 3 x4 Factorial experiment in Completely Randomized Design.

Place and Duration of Study: The study was conducted at the Federal University of Technology, Akure wood laboratory and the study lasted for 6 months.

Methodology: Wood samples were thermally treated at the temperature of 120, 140, 160 and 180°C, for different durations of 1, 1.5 and 2 hours in a muffle furnace. The planks were air-dried to reduce the moisture content and then machined into the required dimensions in the direction parallel to grain with a circular saw. Thirty-nine defect-free samples of dimensions 20 mm × 20 mm × 60 mm were prepared for dimensional stability and compression test, static bending tests and the hardness tests to make a total of 117 samples.

*Corresponding author: E-mail: eaiyiola@futa.edu.ng;

Results: The result showed that the average weight loss of the treated wood samples varied from 3.79% at 120°C for 1 hour to 7.51% at 180°C for 2 hours. The treatment led to reduction in density from 528 to 459 kg/m³ at 180°C for 2 hours. The heat treatment also led to reduction in water absorption and volumetric swelling of the treated samples. The mean value for Modulus of elasticity (MOE) ranges from 2.17x10³ N/mm² to 2.96 x 10³ N/mm² for the treated samples while the untreated was 2.22x10³ N/mm². Heat treatment brought about improvement in the maximum compressive strength and the Janka hardness parallel to the grain of wood samples. The value of compressive strength increased from 26.58 N/mm² to 41.71 N/mm² and hardness from 69.24 N to 75.5 N. It can therefore be concluded that thermal modification greatly enhanced the dimensional stability and mechanical properties of wood samples.

Keywords: Compression; Daniella oliveri; heat treatment; hardness; modulus of elasticity; weight loss.

1. INTRODUCTION

The heat treatment method for modifying wood enhances its dimensional stability and is more environment-friendly as compared to other methods like chemical treatments [1,2,3,4]. Although, heat treatment results in significant changes in the wood properties, but it also causes undesirable reductions in the mechanical properties of wood such as the Modulus of Elasticity (MOE). Different species of wood react differently to heat treatment based on their individual compositional variations, so it is important to determine the optimal conditions (such as duration and temperature) for heat treatment to achieve the best balance of physical and mechanical properties. To achieve this, tests must be conducted to determine the value of the properties of wood samples that have been heat treated at different durations and temperatures. As a result of heat treatment, the chemical composition of wood is altered; the hemicelluloses are most affected, and cellulose is somewhat resistant to chemical alteration [5]. Other changes that occur as a result of heat treatment include increased lignin content, increased dimensional stability due to cross-linking in the lignin, the destruction of some of the sorption sites, improved durability, decreased mechanical properties such as static and dynamic bending strength and tensile strength, lower equilibrium moisture content, and darker colour as reported in previous studies [5]. Many studies have been conducted to determine the influence of heat treatment on physical properties of different wood species using a wide range of treatment conditions. The difference in the species and the different treatment schedules causes changes in the physical properties, such as mass loss, anti-swelling efficiency, and equilibrium moisture content, produce a wide range of values. Mass loss is a determinative factor of the result of heat treatment, that is, the

greater the mass loss, the greater the effects on the physical and mechanical properties. [3] reported that there is a significant relationship between mass loss and compression strength of wood and [6] also observed that there is a significant relationship between mass loss and equilibrium moisture content of wood. [7] in his studies determined the density and shrinkage behaviour of *E. grandis* wood where he showed that the thermal rectification process (only when a temperature of 200°C was used) influenced shrinkage properties of wood significantly. [8] studied the changes in chemical composition that occurred when Eucalyptus and Pinus wood were subjected to heat treatment at 120, 140, 160, 180°C, and the results showed that the arabinose, mannose, galactose, and xylose contents of the treated wood decreased significantly at 160 and 180°C. [9] reported the physical and mechanical properties of thermally-modified *E. grandis* wood, and the results showed decrease in mass, equilibrium moisture content, volumetric shrinkage to be 6.7, 21.5 and 23.2% respectively, at a temperature of 180°C and a duration of 2.5 h. In previous studies, some properties of heat treated *E. grandis* wood were found to decrease as a result of heat treatment; these include mass and equilibrium moisture content which gave different values [4].

Therefore, this study focused on the effect of heat treatment on *Daniella oliveri* wood at different temperatures and durations on its dimensional stability (absorption and swelling), Moisture content (MC), the weight loss and mechanical properties of wood.

2. MATERIALS AND METHODS

2.1 Sample Preparation

The samples for this study were obtained from a local sawmill in Akure, Ondo State, Nigeria and

the planks were air-dried to reduce the moisture content and then machined into the required dimensions in the direction parallel to grain with a circular saw. Thirty-nine defect-free samples of dimensions 20 mm × 20 mm × 60 mm were prepared for dimensional stability and compression test. For the evaluation of static bending strength tests (modulus of rupture and modulus of elasticity), thirty-nine specimens of dimensions 20 mm × 20 mm × 300 mm were prepared. Another thirty-nine specimens of dimensions 30 mm × 30 mm × 25 mm were prepared for hardness test. In total, 117 specimens, both treated and untreated were prepared and correctly labelled. The specimens were oven dried at 103 ± 2 °C until constant weight was achieved. Thereafter, the weights and dimensions of the specimens were measured to determine the moisture content of the samples using;

$$MC(\%) = \frac{\text{Wet weight} - \text{Oven dried weight}}{\text{Oven dried weight}} \times 100\% \quad (1)$$

2.2 Thermal Modification Process

The heat treatments were conducted in a Muffle furnace. The conditioned specimens were treated at temperatures of 120, 140, 160 and 180°C for 1, 1.5 and 2 hr. The wood samples were introduced into the furnace and then ramped to the temperature at which the actual heat treatment occurred. At the end of each treatment period, the samples were removed from the furnace and cooled in a desiccator containing silica gel. Thereafter weights and dimensions were determined to get the weight change. The weight loss (WL), was determined using equation (2):

2.2.1 Weight loss

$$WL(\%) = \left(\frac{W_o - W_t}{W_o} \right) \times 100 \quad (2)$$

Where: WL (%) is the weight loss, W_o (g) is the oven-dry weight of specimens before the treatment and W_t (g) is the dry weight of specimens after the thermal treatment.

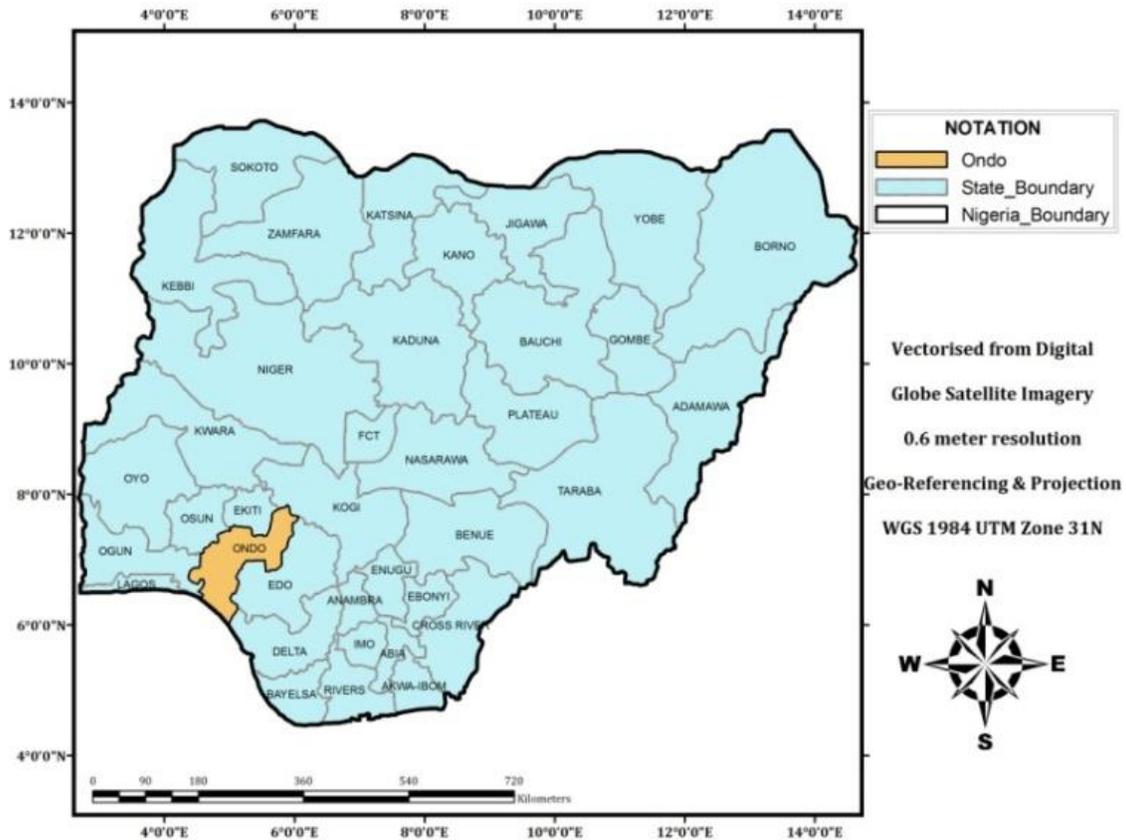


Fig. 1. Map of Nigeria showing Akure and Ondo State (Study location). Adapted from Olamiju & Oyinloye (2015)

2.2.2 Dimensional stability tests

Treated and untreated wood samples were submerged in distilled water in a stainless steel container. A metal screen was placed over the samples to hold the samples approximately 2.5 cm below the surface. Water absorption and thickness swelling were assessed after 24, 48 and 72 hours of water soaking. From the measurement of the dimensions and weights of specimens, the properties measured include Density, Water Absorption (WA), and Volumetric Swelling (S) which were then calculated in accordance with ASTM standard for testing small clear samples [10].

2.3 Mechanical Properties Tests

2.3.1 Static bending

For evaluation of static bending strength, three points' flexural tests were performed on both untreated and treated samples in accordance with [10]. The dimension of wood samples used for the test was 20 mm × 20 mm × 300 mm. Three replicates were tested for each treated wood sample on an Instron 5500R-1137 Universal Test Machine equipped with a 454 kg load cell. Data were collected and processed using Statistical Package for Social Sciences (SPSS) in which Modulus of Elasticity (MOE) and Modulus of Rupture (MOR) were calculated using the software.

$$MOE = \frac{PL^3}{4ywh^3} \quad (N/mm^2) \quad (3)$$

$$MOR = \frac{3PL}{2wh^2} \quad (N/mm^2) \quad (4)$$

Where;

P is the load, L is the length, y is the deflection, w is the width and h is the depth or thickness of the specimen.

2.3.2 Determination of maximum compressive strength (MCS) parallel to grain

The Maximum Compressive Strength (MCS) parallel to grain was determined using sample size of 20 mm x 20 mm x 60 mm in accordance with [10]. This was carried out with the use of Instron 5500R-1137 Universal Testing Machine with a load applied at a rate of 280 N. The values obtained were used to calculate the compressive strength using the equation below.

$$\sigma_c = \frac{P}{bd} \quad N/mm^2 \quad (5)$$

σ_c = Maximum Compressive Strength in N/mm²

b = width in mm

d = depth in mm

P = Load in Newton

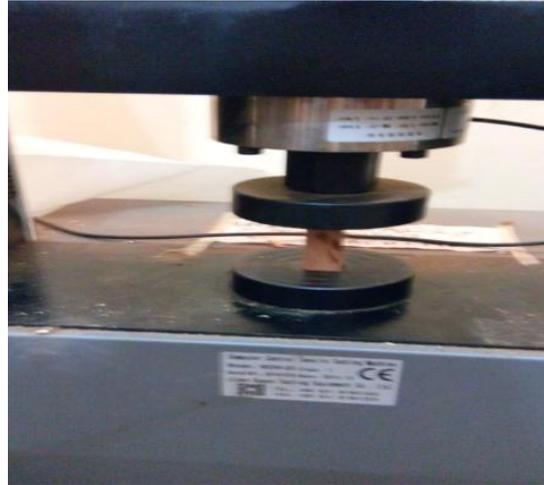


Fig. 2. Maximum Compressive Strength (MCS) parallel to grain test on a Universal Testing Machine

2.3.3 Hardness test

A Janka hardness tester with a modified, diameter 11.3 mm ball (projected area 1 cm²) was used to determine the hardness of specimens. One centralised penetration was made on the tangential and radial face by continuously applying the load at a rate of 6.6 mm/ min. The load at which the ball attained half its penetration was recorded as the hardness (N) of the wood specimen.



Fig. 3. Determination of Hardness using Janka tester

3. RESULTS AND DISCUSSION

3.1 Physical Properties of Thermally Modified *Daniella oliveri*

Tables 1 and 2 show the physical properties of thermally modified wood of *Daniella oliveri* at each treatment duration. The weight loss values were found to differ among the different treatment temperatures and time. The values of weight loss of the treated wood varied from 3.79% at 120°C for 1 hour to 7.51% at 180°C for 2 hours. The highest percentage weight loss was obtained for the treated samples at 180°C for 2 hours. Similar results were reported by [7] who found that the thermal treatment of *E. grandis* at 200°C caused an increase of 25% in weight loss. It is obvious from the table that the mass loss increased with increasing temperature and treatment time. [4] found that the weight loss was inversely proportional to increase in temperature and length of thermal treatment. The results of density decreased for treated wood samples as compared to control samples and also the values of density decreased from 528 Kg/m³ at 120°C for 1 hour to 459 Kg/m³ at 180°C for 2 hours while the control was 693 Kg/m³. Table 2 shows the water absorption and volume swelling at different immersion time. Moisture uptake reduced for treated wood samples than for control samples (Table 2). This might be attributed to the chemical decomposition of carbohydrates occurring at treatment temperature which are responsible for the wood-water interactions. The reduction effect of the thermal treatment on the water absorption was more remarkable compared to the long immersion time as shown in Table 2. It should be noted that the water absorption values of heat-treated wood were higher than those of untreated wood samples for each of the three immersion

period. The result shows that thermally treated samples are more effective in moisture uptake reduction in short duration exposure to water, but loses its relative influence with prolonged time, which can be attributed to a lowered fibre saturation point of thermally treated wood. At the early stage of water soaking, water is located within the cell wall until the fibre saturation point is reached. After this point, water is located in the cell lumen as free water. The water absorption values increased with increasing temperature of thermal treatment in accordance with the work of [11].

The study demonstrates that the thermally modified *D. oliveri* wood showed reductions of 13.38% at 160°C for 1.5 hours to 5.41% at 180°C for 2 hours in volumetric swelling when soaked in water for 24 hours compared with the values found for untreated wood (29.32%).

Similar results were presented by [7], who found that the thermal treatment of *E. grandis* for 200°C caused a decrease of 25% in volumetric shrinkage, and by [9], who concluded that wood of *E. grandis* thermally modified at 220°C presented improvement in the volumetric swelling. The effects of thermal treatment on the physical properties of *D. oliveri* wood showed that temperatures up to 180°C for 2 hours led to improvement in dimensional stability without losses of material. The results of this study agreed with those reported by [9,12,13] for thermally modified wood of other species. Also, [14] reported a reduction in some physical properties, oven-dry density, air-dry density and swelling of wood. [15] also reported that wood subjected to high temperature loses its capacity to reabsorb water in contrast to the hydrophilic behavior of the conventionally dried wood.

Table 1. Mean values of physical properties of thermally modified *Daniella oliveri*

Treatment (°C)	Time (min)	Density (Kg/m ³)	M.C. (%)	Weight loss (%)
Control	-	693.0±118.56	12.83±6.04	-
120	60	528.0±95.98	8.77±1.65	3.79±2.01
120	90	521.0±44.91	6.61±0.58	4.91±0.86
120	120	496.0±23.84	6.56±0.70	5.55±0.25
140	60	509.0±56.69	8.43±3.35	3.88±2.60
140	90	514.0±40.81	9.36±5.30	5.63±1.01
140	120	489.0±33.07	6.18±0.33	5.44±0.44
160	60	500.0±23.38	6.51±0.89	5.98±0.57
160	90	463±22.22	6.59±0.33	6.56±0.37
160	120	492±2.18	7.00±1.33	6.35±0.33
180	60	516±23.04	6.75±1.68	7.45±0.61
180	90	474±28.40	6.85±0.86	7.13±0.49
180	120	459±13.43	5.90±0.28	7.51±0.22

Table 2. Mean values of physical properties of thermally modified *Daniella oliveri*

Treatment (°C)	Time (min)	WA (%) (24h)	WA (%) (48h)	WA (%) (72h)	VS (%) (24h)	VS (%) (48h)	VS (%) (72h)
Control	0	73.90±36.79	88.2±39.2	95.3±43.7	29.3±12.40	32.40±1.93	37.14±4.08
120	60	98.20±14.64	110.0±15.2	113±14.49	11.14±6.03	13.40±3.34	25.07±10.63
120	90	99.60±8.72	111.0±5.4	119±7.16	10.02±5.73	13.39±6.08	15.60±6.43
120	120	104.01±3.49	118.0±2.3	123±1.33	8.09±2.62	9.53±3.05	14.15±3.19
140	60	101.02±3.41	114.0±6.8	118±7.19	9.43±1.96	11.47±4.18	15.16±3.79
140	90	74.90±28.08	90.4±28.3	97.3±28.37	7.91±3.17	13.44±6.93	14.03±2.87
140	120	94.10±6.29	111.0±28.2	116±7.96	9.57±3.32	11.72±1.68	16.37±1.38
160	60	93.03±33.06	106.0±29.3	116±30.97	12.27±2.65	9.48±2.02	14.09±4.12
160	90	98.02±9.53	113.0±6.5	120±9.65	12.70±1.80	9.26±2.08	14.06±0.38
160	120	88.03±7.87	103.8±7.9	111±4.34	13.38±0.05	9.79±0.61	16.17±0.91
180	60	75.21±24.10	92.7±21.3	100±21.38	12.74±2.28	16.54±1.67	16.11±1.56
180	90	74.67±8.60	93.9±6.1	103±6.13	8.39±5.68	12.13±5.69	14.34±3.15
180	120	66.3±10.21	85.9±12.8	95.3±15.5	5.41±0.98	9.03±1.61	9.86±1.58

Table 3. Mean values of mechanical properties of thermally modified *Daniella oliveri*

Treatment (°C)	Time (min)	MOR(N/mm ²)	MOE(N/mm ²)	Compression test(N/mm ²)	JankaHardness test(N)
Control	0	46.43±7.10	2220±675.7	24.92±7.69	68.34
120	60	42.75±19.12	2440±956.6	26.58±8.84	69.24
120	90	43.90±6.96	2630±184.3	36.60±4.11	69.28
120	120	51.91±3.77	2960±244.7	35.93±3.65	71.8
140	60	49.95±2.79	2760±93.3	29.89±1.24	71.95
140	90	48.65±2.67	2490±154.0	32.09±0.91	73.37
140	120	53.79±2.22	2490±35.1	40.46±9.10	74.62
160	60	40.64±0.65	2870±383.8	41.71±7.68	72.05
160	90	43.70±11.18	2650±687.6	31.92±1.88	72.85
160	120	33.89±10.21	2170±706.1	29.50±6.37	70.25
180	60	45.56±3.34	2790±136.1	35.20±2.25	75.5
180	90	35.55±23.70	2430±902.8	25.39±11.03	73.97
180	120	39.34±5.96	2350±454.9	29.41±36.94	74.07

3.2 Mechanical Properties of Thermally Treated *Daniella oliveri*

The MOR, MOE, Compression test and Janka hardness tests are shown in the Table 3. It was observed that the modulus of rupture values of the treated samples ranged from 53.79 N/mm² at 140°C for 120 mins to 33.89 N/mm² at 160°C for 120 mins and later increased to 45.56 N/mm² at 180°C for 60 mins compared to untreated sample which had a value of 46.43 N/mm². The decrease in strength properties of wood after thermal treatment can be explained by the rate of thermal degradation and losses of substances after treatment [11]. The decrease in strength is mainly due to the depolymerisation reactions of wood polymers [16].

Lowest values were recorded for Modulus of Rupture at the treatment of 160°C for 2 h. The Janka hardness parallel to the grain increased from 69.24 N to 75.5 N after heat treatment and the maximum hardness value was obtained as 75.5 N at 180°C for 1 h. These results can be explained with loss in cell wall material and hemicelluloses degradation at high treatment temperature after heat treatments. Decrease in strength is mainly due to the de-polymerization reactions of wood polymers [17]. Furthermore, the wood density plays a key role on the mechanical properties of the wood, similar results for heat treated wood about reductions in mechanical strength properties were reported by [1,18].

The effect of heat treatment on the elastic properties of wood is minimal, although there was an increase in the value of the MOE during the bending test. Degradation of the hemicelluloses, disrupting the load-sharing capacity of the lignin-hemicelluloses matrix, and increase of the relative amount of crystalline cellulose could contribute to the increase of the MOE. The Modulus of Elasticity of the treated samples range from 2.17×10^3 N/mm² to 2.96×10^3 N/mm² compared to the control (2.22×10^3 N/mm²). The increased cross linking of the lignin network probably affects the MOE, since it is expected that an increased cross linking improves the rigid structure around the cellulose microfibrils and the strength characteristics of the middle lamella. Furthermore, heat treated wood is less hygroscopic than untreated wood (it contains less bound water in the cell wall), which affects the MOE making wood less pliable [19].

The maximum compressive strength of wood samples parallel to grain increased from 26.58 N/mm² to 41.71 N/mm² and decreased after heat treatment. The increase of the compressive strength in longitudinal direction might be due to a lower amount of bound water in heat treated wood, however it is expected that the amount of bound water must be higher to affect the strength properties. Generally, the values of the different strength tests increased after heat treatment. [20] reported similar result for wild cherry and reported that the Compression strength values of wild cherry wood samples were decreased with increasing treatment time. It is clear from Table 3 that there is slight increase in the hardness number of wood with a decrease in the moisture content as the temperature increased with time [21].

4. CONCLUSION

This study revealed that water absorption and volumetric swelling of the wood species studied decreased with increased heat treatment intensity. Thermal treatment resulted in reduction in swelling and water absorption of the samples to great extent.

The weight loss of the specimens increases while density decreases with increased heat treatment at a temperature of 180°C for duration of 2 hours. The density and weight loss decreased for the milder treatments, while as the duration increases, the decrease tends to be slower and more gradual, which indicates that treatment duration of 2 hours reduces the water re-absorbing capacity and hygroscopic properties of *Daniella oliveri* wood. However, temperature of 180°C for 2 hours could be applied to wood where physical properties are preferred. The Modulus of Elasticity and Modulus of Rupture of the wood species decreased with heat treatment. The Maximum Compression strength parallel to grain decreased with heat treatment. The hardness increased with increased in heat treatment. Therefore, heat treated wood can be utilized with appropriate heat treatment time and temperature without any loss in strength values in areas, where woodwork such as parquet flooring and decorative purpose, stability are important.

COMPETING INTERESTS

Authors have declared that no competing interests exist.

REFERENCES

1. Poncsak S, Kocafe D, Younsi R. Improvement of the heat treatment of Jack pine (*Pinus banksiana*) using thermo-wood technology. *Eur J. Wood Prod.* 2006;9(2):281-286.
2. Kocafe D, Poncsak S, Boluk Y. Effect of thermal treatment on the chemical composition and mechanical properties of birch and aspen. *Bior.* 2008;3(2):517-537.
3. Gunduz G, Korkut S, Deniz A, Bektar L. The density, compression strength and surface hardness of heat treated hornbeam (*Carpinus betulus*) wood. *Mad. Cien y Technol.* 2009;11(1):61-70.
4. Garcia RA, Carvalho AM, Latorraca JV, Matos JL, Santos WA, Silva RF. Nondestructive evaluation of heat-treated *Eucalyptus grandis* Hill ex Maiden wood using stress wave method, *Wood Sci. Technol.* 2012;46:41-52.
Available:<http://dx.doi.org/10.1007/s00226-010-0387-6>
5. Esteves BM, Pereira HM. Wood modification by heat treatment: A review. *Bior.* 2009;4(1):370-404.
Available:<http://www.bioresources.com>
6. Esteves B, Marques AV, Domingos I, Pereira H. Influence of steam heating on the properties of pine (*Pinuspinaster*) and eucalypt (*Eucalyptus globulos*) wood. *Wood Sci Technol.* 2007;41(3):193-207.
Available:<http://dx.doi.org/10.1007/s00226-006-00990>
7. Brito JO, Garcia JN, Bortoletto GJ, Pessoa AM, Silva PH. Densidade básica e retratibilidade da madeira de *Eucalyptus grandis*, submetida a diferentes temperaturas de termoretificação. *Cerne.* 2006;12(2):182-188.
8. Brito JO, Silva FG, Leao MM, Almeida, G. Chemical composition changes in Eucalyptus and pinus woods. *Bior Technol.* 2008;99:8545-8548.
Available:<http://dx.doi.org/10.1016/j.biortech.2008.03.069>
9. Calonego FW, Severo ET, Ballarin AW. Physical and mechanical properties of thermally modified wood from *E. grandis*. *Eur J. Wood Prod HolzalsRoh-und-Werkstoff.* 2012;70(4):453-460.
Available:<http://dx.doi.org/10.1007/s00107-011-0568-5>
10. ASTM - American Society for Testing and Materials. ASTM D-4442-92, Standard test methods for direct moisture content measurements of wood and wood-Base materials. West Conshohocken. 2009;22.
11. Dundar T, Büyüksarı U, Avcı E, Akkılıç H. Effect of heat treatment on the physical and mechanical properties of compression and opposite wood of Black pine. *Bior.* 2012;7.
DOI: 10.15376/biores.7.4.5009-5018
12. Bhuiyan TR, Hirai N, Sobue N. Effect of intermittent heat treatment on crystallinity in wood cellulose. *J Wood S.* 2001;47:336-341.
Available:<http://dx.doi.org/10.1007/BF00766782>
13. Metsä-Kortelainen S, Anitikainen T, Viitaniemi P. The water absorption of sapwood and heartwood of Scots pines and Norway spruce heat-treated at 170°C, 190°C, 210°C and 230°C. *Eur J Wood Wood Prod/HolzalsRoh- und Werkstoff.* 2005;64:192-197.
14. Korkut DS, Guller B. The effects of heat treatment on physical properties and surface roughness of red-bud maple (*Acer trautvetteri* Medw.) wood. *Bior Technol* 2008;99(8):2846–51.
15. Kocafe D, Younsi R, Chaudry B, Kocafe Y. Modelling of heat and mass transfer during high temperature treatment of aspen. *Wood Sci. Technol.* 2006;40:371-391.
16. Wikber H, Maunu SL. Characterization of thermally-modified hard- and softwoods by 13C CPMAS NMR. *Carbon Poly.* 2004;58:p461-466.
Available:<http://dx.doi.org/10.1016/j.carbpol.2004.08.008>
17. Kotilainen R, Toivannen T, Alén R. FTIR monitoring of chemical changes in softwood during heating. *J. Wood Chem. Technol.* 2000;20(3):307-320.
18. Santos JA. Mechanical behavior of Eucalyptus wood modified by heat. *Wood Sci. Technol.* 2000;34:39-43.
Available:<http://dx.doi.org/10.1007/s00226-0050006>
19. Kubojima Y, Okano T, Ohta M. Bending strength and toughness of heat treated wood. *J. Wood Sci.* 2000;46(1):8–15.
Available:<http://dx.doi.org/10.1007/BF00779547>

20. Suleyman K, Ayhan A. Evaluation of physical and mechanical properties of wild cherry wood heat-treated using the thermo-wood process. *Mad. Cien y Tecnolo.* 2015;17(1):171–178.
21. Hsawa M, Miyajima H. Deformation of wood due to ball indentation and its measuring method. *Memo. Fac. Agr., Hokkaido Univ.* 1954;2(1):1-5. (Japanese with English Summary, p. 5).

© 2019 Iyiola et al.; This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Peer-review history:
The peer review history for this paper can be accessed here:
<http://www.sdiarticle3.com/review-history/48727>